

## INTRODUCTION

**SCS7\*** is Asahi's latest lead free alloy development. As an enhanced tin/copper lead free alloy, it is highly recommended to directly replace existing SnCu0.7 solder. This alloy not only exhibits the excellent ductility of SnCu0.7 solder, it also possesses superior mechanical strength both in ambient and high temperature environments. SCS7's fatigue resistance is now comparable to tin/lead solder and as such, SCS7 has addressed the fundamental concerns of SnCu alloys.

SCS7 (CLF5013) lead free no clean core flux solder wire is formulated using purest raw chemicals together with halide-free materials, which guarantees absolute flux core continuity and consistency in solder properties. It provides excellent instant wetting action and superior solderability on a variety of surface finishes.

## SPECIFICATIONS

Item	Specifications	Test Standards
Flux Content	3.0 +/- 0.5 wt%	Singapore Asahi
Density of Core Flux @ 25°C	0.866	Singapore Asahi
Halide Content	0 wt%	IPC-TM-650 2.3.35B JIS Z 3197: 1999 8.1.4.2.2
Water Extract Resistivity	>1.0 x10 <sup>4</sup> Ω-cm	JIS Z 3197: 1999 8.1.1
Surface Insulation Resistance (Raw Flux) (85°C, 85 %RH, 1000hrs)	>1x10 <sup>8</sup> Ω >1 x10 <sup>11</sup> Ω	IPC-TM-650 2.6.3.3 JIS Z 3197: 1999 8.5.4
Copper Corrosion Test	Pass	IPC-TM-650 2.6.15 JIS Z 3197: 1999 8.4.1
Copper Mirror Test	Classified as "M", Pass	IPC-TM-650 2.3.32 JIS Z 3197: 1999 8.4.2
Flux Activity Classification	ROM0	IPC J-STD-004A
Spread Factor	>80% (SCS7)	JIS Z 3197: 1999 8.3.1.1
Residue Dryness Test	Dry	JIS Z 3197: 1999 8.5.1
Residue Appearance	Transparent & Minimal	Visual

\* UK Patent No. GB2406101

## ALLOY SPECIFICATION

<b>Main Composition</b>		
		<b>IPC J-STD-006B Specs (Wt %)</b>
Tin	Sn	Remainder
Copper	Cu	0.7 +/- 0.1
Silicon	Si	0.02 +/- 0.01
<b>Contamination</b>		
Silver	Ag	0.10 max
Aluminium	Al	0.005 max
Arsenic	As	0.03 max
Gold	Au	0.05 max
Bismuth	Bi	0.10 max
Cadmium	Cd	0.002 max
Iron	Fe	0.02 max
Indium	In	0.10 max
Nickel	Ni	0.01 max
Lead	Pb	0.05 max
Antimony	Sb	0.05 max
Zinc	Zn	0.003 max

## PHYSICAL PROPERTIES

	<b>SCS7</b>	<b>SnCu0.7</b>	<b>Sn63Pb37</b>
Melting Temperature	227°C	227°C	183°C
Coefficient of Thermal Expansion	22.7 $\mu\text{m}/\text{m}^\circ\text{C}$	19.3 $\mu\text{m}/\text{m}^\circ\text{C}$	23.3 $\mu\text{m}/\text{m}^\circ\text{C}$
Density	7.30 $\text{g}/\text{cm}^3$	7.31 $\text{g}/\text{cm}^3$	8.40 $\text{g}/\text{cm}^3$

## MECHANICAL PROPERTIES

	<b>SCS7</b>	<b>SnCu0.7</b>	<b>Sn63Pb37</b>
Tensile Strength	45.83 MPa	44.35 MPa	52.54 MPa
Yield Strength	38.78 MPa	37.31 MPa	39.28 MPa
Max Percent Strain	68.16 %	58.31 %	67.38 %
Energy to Yield Point	0.203 J	0.100 J	0.164 J
Energy to Break Point	18.05 J	15.28 J	18.98 J
Toughness	25.54 MPa	21.62 MPa	26.85 MPa
Cycle Fatigue Resistance, $N_f$	3000 - 3500	1125	3650
<b>Creep Resistance</b>			
Load at 1kg @ 145°C	>40hrs	N.A.	>27 hrs

## APPLICATION

SCS7 (CLF5013) lead free no clean core flux solder wire is easy to use for automatic, manual, rework, point and brush soldering. For the best soldering results, the recommended parameters are shown:

Solder Iron Tips: All Types especially the tapered types  
Soldering Temp: > 350°C  
Soldering Time: 1 - 3 secs

- Keep solder iron tips clean.
- Tinned iron tips before use.
- Wear gloves when soldering to avoid contaminating the wire.

(Note: Soldering parameters are dependent on tip type, soldering station wattage configuration, wire diameter and type of applications.)

## PACKAGING

SCS7 (CLF5013) lead free no clean core flux solder wire is commonly available in various diameters such as 0.25, 0.3, 0.4, 0.5, 0.6, 0.8, 1.0, 1.2, 1.6 and 2.0 mm. For different diameters, please specify your requirements.

Packaging	0.03kg	0.10kg	0.20kg	0.25kg	0.50kg	1.0kg
Diameter (mm)	0.25	0.3	0.4	0.5 to 2.0	0.5 to 2.0	0.8 to 2.0

## RESIDUAL REMOVAL

Since the residues are transparent, minimal, dry, non-tacky and practically inert after soldering, removal is usually not necessary. For assemblies that require cleaning, the residue of SCS7 (CLF5013) lead free no clean core flux solder wire can be completely removed by any solvent type flux cleaner available in the market.

## SAFETY

Wear a chemical mask if the operators are allergic to the fumes released during soldering. For more information, please refer to Material Safety Data Sheet.

## STORAGE

Store the solder wire in a cool, dry environment. Wrap up the solder wire when not in use to reduce exposure to environment. SCS7 (CLF5013) lead free no clean core flux solder wire can be kept for 2 years if proper storage conditions are observed.

---

### SINGAPORE ASAHI CHEMICAL & SOLDER INDUSTRIES PTE LTD

47 Pandan Road S(609288)  
Tel: 6262-1616 Fax: 6261-6311  
Website: <http://www.asahisolder.com> E-mail: [sales@sinasahi.com.sg](mailto:sales@sinasahi.com.sg)

## TEST ANALYSIS

Various tests were conducted to evaluate the performance and reliability of CLF5013 core flux.

### HALIDE CONTENT

This test is to determine the amount of halide present in the core flux.

#### Method:

By titration method with end point determination. The % chlorides calculated based on the following formula:

$$\text{Halides, as \% Chlorides} = \frac{3.55 \text{ VN} \times 100}{\text{ms}}$$

#### Result:

Halide Content = 0 wt%.

### WATER EXTRACT RESISTIVITY

This test measures the resistivity of the flux constituents.

#### Method:

- Take an amount of the flux containing solid portion equivalent to 0.05 +/- 0.005g as the sample.
- Put the sample in a beaker with 50ml of purified water. Cover the beaker with a watch glass.
- Heat and boil it for about 5 min, and continue heating for about 1 min.
- Cool the beaker for about 10 secs at room temperature, then place beaker in a water bath of about 20°C to obtain the test solution.
- Immediately measure the resistance of this water solution using a conductivity meter.

#### Result:

The test result obtained is  $1.8 \times 10^5 \Omega\text{-cm}$ , which exceeds the minimum required specific resistance of  $1.0 \times 10^4 \Omega\text{-cm}$ .

## SURFACE INSULATION RESISTANCE


It determines the surface insulation properties of the flux on the finished product. Thus, it determines the reliability of the residue if left on board without cleaning.

### Test Conditions (IPC-TM-650 2.6.3.3)

Humidity : 85 %RH  
Temperature : 85°C  
Duration : 1000hrs  
Bias Voltage : +50V D.C.  
Applied Voltage : -100V D.C.  
Test Coupon : IPC-B-24

### Result:

#### Surface Insulation Resistance of CLF5013 (IPC)

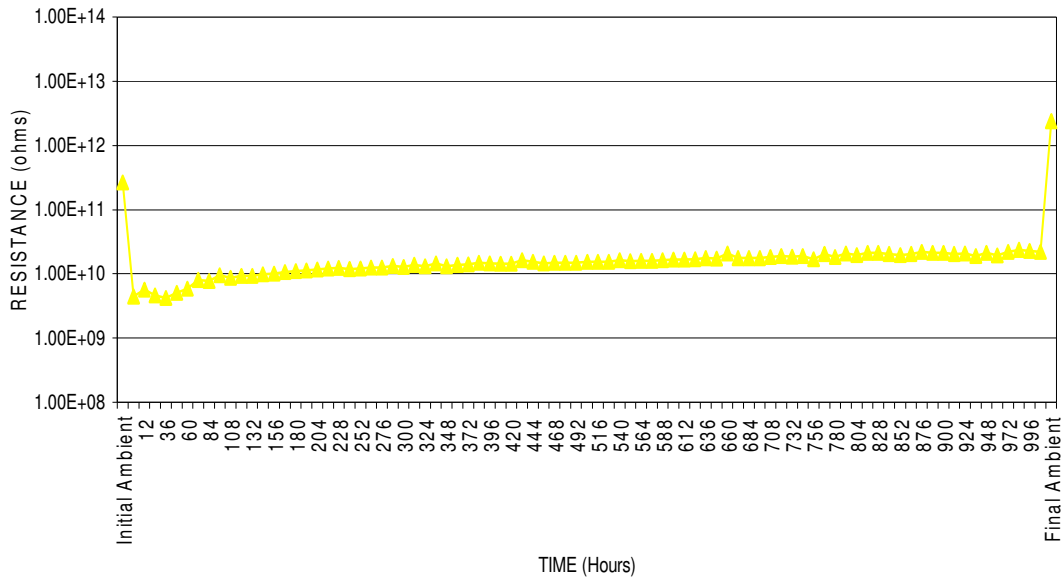


Surface Insulation Resistance:  $> 1 \times 10^9 \Omega$ , passed.

### Test Conditions (JIS Z 3197: 1999 8.5.4)

Humidity : 85 %RH  
Temperature : 85°C  
Duration : 1000hrs  
Bias Voltage : +50V D.C.  
Applied Voltage : -100V D.C.  
Test Coupon : JIS C 6480

## **Result:**

### **Surface Insulation Resistance of CLF5013 (JIS)**

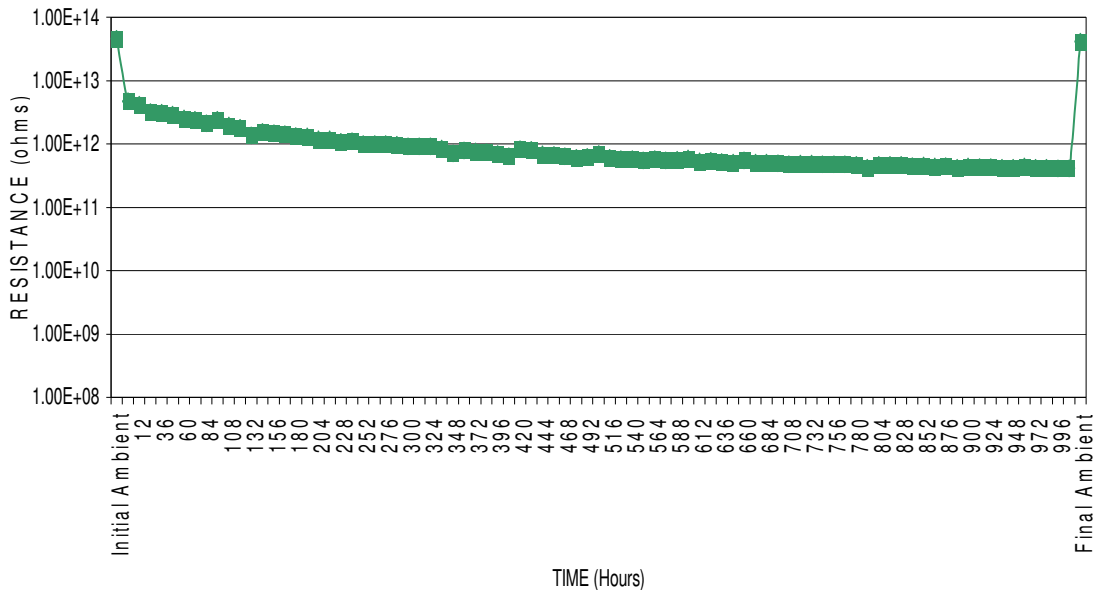

Surface Insulation Resistance:  $> 1 \times 10^{11} \Omega$ , passed.

## **COPPER CORROSION TEST**

Evaluate the extent of corrosion due to the flux residue after soldering under moisture.

### **Method:**

- Weigh 1 gram of solder and make into a coil with a 3mm mandrel.
- Place the cleaned copper coupon on the surface of solder bath set to 250°C.
- Let the specimen remain on the solder bath surface for 5 secs after solder fusing.
- Allow the specimen to cool for 15mins.
- Place the specimen in a humidifier set at 40°C, 90 %RH for 96hrs.
- Inspect the specimen for growth of corrosive compounds that are assumed to be green, bluish green or white.

### **Result:**

No drastic change in appearance of copper under the residue or at the flux boundary. CLF5013 has passed the corrosion test.

## COPPER MIRROR TEST

This test provides a visual check on the corrosive effect of the flux on the substrate.

### Method:

- Place one drop of test flux onto the copper mirror.
- Keep copper mirror at 23 +/- 2°C & 50 +/- 5 %RH for 24 hrs.
- Remove test flux by immersion in clean 2-propanol.

### Result:

The result showed that CLF5013 is classified as "M".

## SPREAD TEST

The purpose of this test is to measure the spread capability of the CLF5013 core flux.

### Method:

- Maintain hot plate temperature at 250°C.
- Place the solder wire (Ø3mm) on a copper coupon.
- Place the coupon on hot plate.
- Measure rate of spread with the formula below:

$$\begin{aligned} \text{Rate of Spread} &= (D-H)/D \times 100\% \\ \text{where } D &= 1.24 \times V^{1/3} \\ V &= \text{Mass} / \text{Specific Gravity} \\ H &= \text{Height of Spread Solder} \end{aligned}$$

### Result:

The result showed that CLF5013 had a spread factor of 80% with SCS7 solder.



## RESIDUE DRYNESS TEST

This test determines the tackiness of the residue after soldering.

### Method:

- Place circular solid solder wire preform on Cu.
- Add 0.035 to 0.040g of solid portion of flux to centre of wire preform.
- Set solder bath temperature at 50  $\pm$ 2 °C above the alloy's liquidus temperature.
- After fusing of solder, leave it for 5 secs.
- Take the test piece out of the bath and cool it for 30 mins.
- Sprinkle powder talc onto the flux residue on the test piece.
- Brush the surface of the residue in the same direction twice and inspect test piece.

### Result:

Powder falls off test piece easily. The flux residue has passed the dryness test.

#### DISCLAIMER OF LIABILITY

"All statements, information and recommendations contained in this catalog are based on data and test results which we consider, to the best of our knowledge and belief, to be reliable and informative to the users but the accuracy and completeness thereof is not guaranteed. No warranty, expressed or implied, statutory or otherwise, is given regarding the use of the information and products contained in this catalog since the conditions and suitability for use, handlings, storage or possession of the products are determined by the users and are therefore beyond our control. We shall not be liable in respect of any liabilities, losses (including consequential losses), damages, proceedings, costs, claims or injuries whatsoever sustained or suffered by the users (including any third parties) in connection with the use of the information, recommendation and the products contained in this catalog."

---

## SINGAPORE ASAHI CHEMICAL & SOLDER INDUSTRIES PTE LTD

47 Pandan Road S(609288)

Tel: 6262-1616 Fax: 6261-6311

Website: <http://www.asahisolder.com> E-mail: [sales@sinasahi.com.sg](mailto:sales@sinasahi.com.sg)